
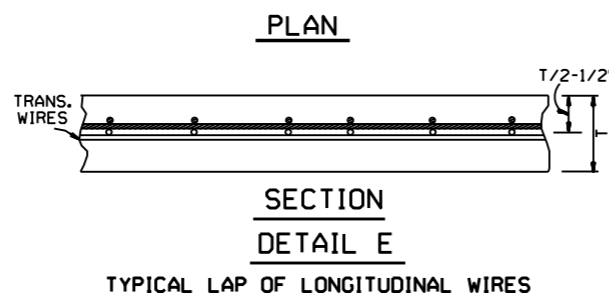
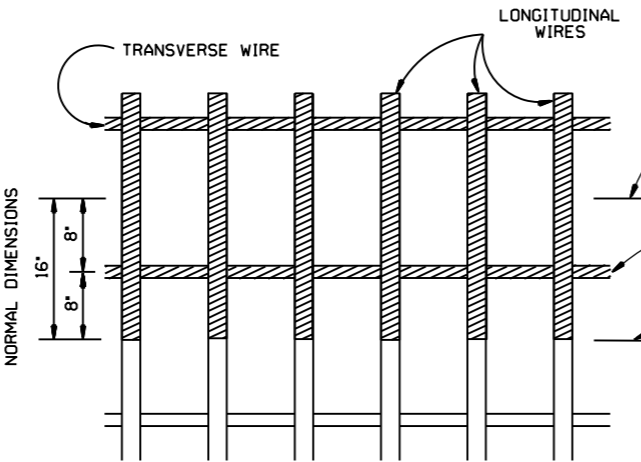


THREE LANE PAVEMENT PLAN
(12' AND 24' PLACEMENT)

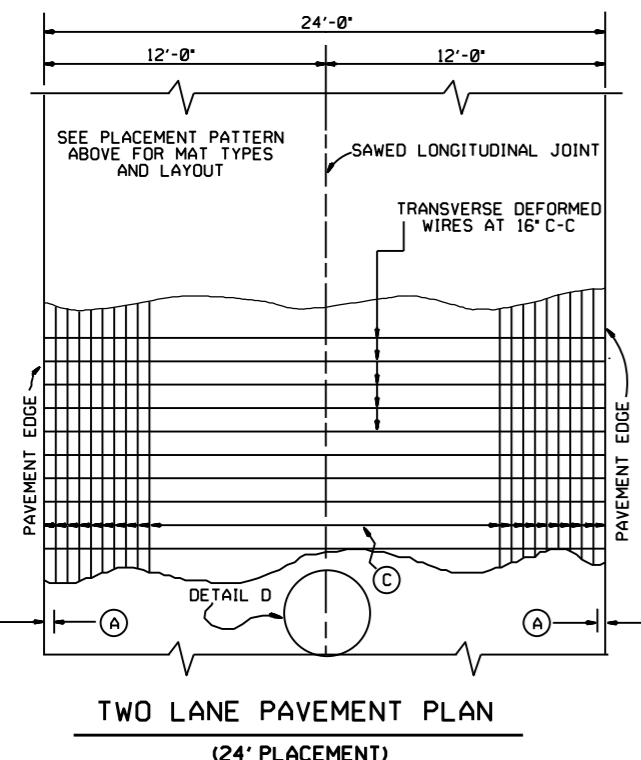

TRANSVERSE CONSTRUCTION JOINT

SAWED LONGITUDINAL JOINT

PAVEMENT THICKNESS (T) IN.	WIRE SIZE	LONGITUDINAL REINFORCEMENT								TRANS. REINF. FOR LONG. CONSTR. JOINT			
		24' PLACEMENT		12' PLACEMENT		ADDITIONAL STEEL TRANS. CONSTR. JOINT		WIRE SIZE	TIE WIRES ③				
		SPACING C-C	STEEL LB/SY	SPACING C-C	STEEL LB/SY	WIRE SIZE	LENGTH IN.			NO. PER LANE	WEIGHT LB./FT. OF WIDTH		
8	D-19.2	2	4	20.59	2	4	20.51	D-19.2	36	16	2.61	D-8	.408
6	D-14.4	2	4	14.90	2	4	14.86	D-14.4	36	16	1.96	D-4	.204

- TABLE NOTE
- ① INCLUDES BOTH LONGITUDINAL AND TRANSVERSE WIRES BASED ON THE WIDTH INDICATED AND AN EFFECTIVE COVER LENGTH OF 32 FEET. (ESTIMATING QUANTITIES INCLUDE SPLICES)
 - ② THIS SHALL BE THE MINIMUM NUMBER OF ADDITIONAL STEEL WIRES TO BE PLACED PER LANE. THE ADDITIONAL STEEL WIRES SHALL BE PLACED EQUIDISTANT BETWEEN TWO REGULAR LONGITUDINAL REINFORCING WIRES AT AS NEAR A UNIFORM SPACING ACROSS THE LANE AS POSSIBLE.
 - ③ AT THE OPTION OF THE CONTRACTOR, #4 BARS X 30 IN. AT 30 IN. C-C MAY BE USED IN LIEU OF THE DEFORMED TIE WIRES AT 16 IN. C-C SHOWN, PROVIDED WRITTEN APPROVAL HAS BEEN RECEIVED FROM THE ENGINEER.

GENERAL NOTES

NO EXPANSION JOINTS WILL BE USED EXCEPT AT STRUCTURAL ENDS OR FIXED OBJECTS AS SHOWN ELSEWHERE IN THE PLANS.

JOINT AND JOINT SEAL DETAILS SHALL BE AS SHOWN ELSEWHERE IN THE PLANS.

CONSTRUCTION JOINTS MAY BE FORMED BY THE USE OF METAL OR WOOD FORMS EQUAL IN DEPTH TO THE NOMINAL DEPTH OF THE PAVEMENT, OR BY THE OTHER MEANS WHICH HAVE BEEN APPROVED BY THE ENGINEER PRIOR TO THEIR USE.

REFER TO TYPICAL SECTION FOR PAVEMENT WIDTH, THICKNESS AND CROWN.

IT IS THE INTENT OF THIS DESIGN THAT THE LONGITUDINAL STEEL BE AT THE CENTER OF THE SLAB. IT SHALL BE THE RESPONSIBILITY OF THE CONTRACTOR TO TAKE ALL NECESSARY PRECAUTIONS TO INSURE THAT THE FINAL POSITION OF THE STEEL IS NOT BELOW THE CENTER OF THE SLAB.

WITHIN ANY AREA BOUNDED BY TWO FEET OF PAVEMENT LENGTH MEASURED PARALLEL TO THE CENTERLINE, AND TWELVE FEET OF PAVEMENT WIDTH MEASURED PERPENDICULAR TO THE PAVEMENT CENTERLINE, NOT OVER 33% OF THE REGULAR LONGITUDINAL STEEL SHALL BE SPLICED.

ALL SPLICES SHALL BE A MINIMUM OF 16" FOR LONGITUDINAL STEEL AND 10" FOR TRANSVERSE STEEL.

AT TRANSVERSE CONSTRUCTION JOINTS THE REGULAR LONGITUDINAL STEEL SHALL EXTEND A MINIMUM OF FOUR FEET ON EITHER SIDE OF THE JOINT.

IF WIDTHS GREATER THAN TYPICAL WIDTHS OCCUR, INDIVIDUAL WIRES MAY BE ADDED TO OBTAIN ADDITIONAL WIDTH, PROVIDED THE C-C SPACING IS NOT EXCEEDED AND LAP REQUIREMENTS ARE MET.

AT ALL LAP SPLICES OCCURRING WITHIN EIGHT FEET BEYOND THE CONSTRUCTION JOINT, IN THE DIRECTION OF PAVING AND FOUR FEET BACK OF THE CONSTRUCTION JOINT, THE LENGTH OF LAP SHALL BE DOUBLE THAT NORMALLY SPECIFIED OR EACH SPLICE SHALL BE STRENGTHENED BY SPLICING IN, SYMMETRICALLY WITH THE LAP, A SIX-FOOT LENGTH OF DEFORMED BAR OF THE SAME NOMINAL SIZE AS THE LONGITUDINAL REINFORCEMENT.

SAWED JOINT AND JOINT SEALANT FOR TRANSVERSE CONSTRUCTION JOINT, LONGITUDINAL CONSTRUCTION JOINT AND SAWED LONGITUDINAL JOINT SHALL CONFORM TO THE DETAILS SHOWN FOR SAWED LONGITUDINAL JOINT ON STANDARD DRAWING CPTJ-6A.

DATE	REVISION	DATE FILMED
3-23-89	ALTERED SAWED JOINT & ADDED NOTE	509-3-23-89
11-3-86	DIMEN'S. OF LONG. JTS.	651-11-3-86
1-4-83	DEPTH OF SAWED TRANSVERSE CONST. JOINT	676-1-4-83
10-2-72	REVISED AND REDRAWN	505-10-2-72

ARKANSAS HIGHWAY COMMISSION

CONCRETE PAVEMENT DETAILS

CONTINUOUSLY REINFORCED

DEFORMED WIRE MAT

STANDARD DRAWING CPCR-2